

Influence of damage on the fractal properties of concrete subjected to pure tension

A. Carpinteri and S. Invernizzi

Department of Structural Engineering and Geotechnics, Politecnico di Torino, Torino, Italy.

Paper received: February 7, 2001; Paper accepted: May 10, 2001

ABSTRACT

In a previous work [1] the authors showed how to acquire the meso-structural characteristics of undamaged concrete-like materials by a peculiar laser equipment [2]. In order to extend the analysis to damaged disordered materials, a new direct tension test equipment has been developed, that minimizes flexural effects by freely rotating boundary conditions. Increasing levels of damage are obtained, after reaching the peak load, by proceeding along the descending strain-softening curve. After the desired damage level is reached, the load is removed and the specimen is cut to permit the laser acquisition of the most damaged zone. The progressive rarefaction of the effective stress-carrying cross section is described by means of fractal concepts. It is worth noting that both the fractal dimension and the measure of the stress carrying cross section decrease after the peak load, and vanish when the specimen is broken apart.

RÉSUMÉ

Lors d'une précédente étude [1], les auteurs ont démontré la possibilité d'apprécier les caractéristiques méso-structurelles des matériaux désordonnés, comme le béton, au moyen d'un dispositif laser [2]. Afin de pouvoir étendre l'analyse à des matériaux désordonnés endommagés, il a fallu mettre au point un équipement d'essai à traction directe, pour minimiser les effets de flexion tout en permettant la rotation des sections des extrémités de l'échantillon. Des niveaux d'endommagement croissants sont obtenus par l'application d'une charge supérieure à la valeur de pic, suivant la courbe décroissante de radoucissement (strain-softening). Une fois le niveau d'endommagement souhaité atteint, la charge est enlevée et l'échantillon est coupé. Le dispositif laser est ainsi capable d'analyser la section la plus endommagée. La rarefaction progressive de la section effective est décrite en utilisant des concepts appartenant au domaine de la géométrie fractale. Il est à la fois possible d'observer la réduction de la mesure de la section effective et la diminution de sa dimension fractale après que la charge appliquée a franchi le pic, jusqu'à l'annulation lorsque les deux moitiés de l'échantillon sont complètement séparées.

1. INTRODUCTION

The disordered microstructure of concrete is responsible for the peculiar features of the fracture phenomenon. Stable crack growth, ductile-brittle transition and size effects are not explicable in the classical framework. Pre-existing pores, debonded zones and microcracks interact with each other in a complex manner. Attempts to describe such behaviours by means of deterministic micromechanics models are deemed to be incomplete or even misleading. Even the most sophisticated measurement of material properties, coupled with the use of most powerful computers, would not succeed in the exact (deterministic) modelization of the fracture phenomenon. The local aspects of cracks (e.g. position, shape, width, growth rate) are neither measurable nor

predictable. On the contrary, the global aspects, e.g. the invariant features, can be put into evidence by approaching the problem from a completely new viewpoint. Cooperative phenomena are nowadays successfully interpreted by means of alternative methods, such as catastrophe theory, fractals, renormalization group theory and chaos dynamics. In particular, the combination of fractal geometry with renormalization provides new insights towards the understanding of concrete fracture [3]. Modelization of the microstructure by means of fractal domains permits to capture the hierarchical and self-organized aspect of damage accumulation and crack propagation. An essential aspect is in fact represented by the lacunarity of the porous microstructure, which represents a random field and explains the size effect on the nominal tensile strength.

Editorial Note

Prof. Alberto Carpinteri is a RILEM Senior Member.

In the present paper, dog-bone concrete specimens subjected to uniaxial tensile tests up to different damage levels are considered. The test-machine is provided with two spherical joints that allow the load to remain centered after the peak load is reached, *i.e.* during the softening regime. An innovative experimental methodology, developed at the Department of Structural Engineering and Geotechnics of the Politecnico di Torino, has been used to analyze the microstructural characteristics of the progressively damaged concrete. By means of a completely automated laser system, the 3D morphologies of concrete can be digitized. This procedure, which yields the effective depth and shape of the pores, permits to overcome the drawbacks and ambiguities of traditional image analysis techniques, where dark particles often confuse with pores.

In previous papers, planar cross-sections of the virgin material were considered, and the pore and void distribution (like the moon-craters distribution) were easily extracted from the (detrended and filtered) laser-scanned topography. That investigation allowed the authors to confirm the lacunar fractal character of the ligament [1], as well as the self-similar character of the pore size distribution, which has been recently assumed in various statistical models of brittle fracture [4]. Now, the same procedure is applied to partially damaged specimens, at different load levels, in order to investigate on the progressive rarefaction of the resisting ligament. As a result of the damage development, not only the measure of the effective stress carrying cross section, but even its fractal dimension decreases.

2. THE CONCRETE TENSION TEST

Although modern displacement servo-controlled closed loop testing machines allow, in principle, to measure the load-displacement curve in the softening regime, concrete testing in tension is particularly difficult. In fact, due to the propagation of cracks after reaching the peak load, the actual section loses its symmetry with respect to the applied load, and disturbing flexural effects arise. In order to avoid such effects completely, three orthogonal actuators can be used to perform uniform displacement tests [5]. Otherwise, it is possible to minimize flexural effects if particular care is taken for the load boundary conditions. If the loading platens are both freely rotating, the load is automatically re-centered (at least to a certain amount) as soon as the section geometry varies due to fracture enucleation. While other authors performed similar tests on notched specimens [6-8], in the present work 18 unnotched dog-bone-shaped concrete specimens are considered (labelled from P01 to P18). It should be mentioned, however, that tensile tests on unnotched specimens can be also found in [9].

Normal portland concrete has been used for casting eighteen dog-bone specimens. Prior to the tensile tests, the material has been characterized from a mechanical point of view, performing standardized compression tests on cubes (see Table 1) and RILEM three-point bending tests [10] (see Table 2). The mean compression strength is equal to

Table 1 - Compression tests					
#	Size [cm]	Size [cm]	Section Area [cm ²]	Peak Load [N]	Compression Strength [MPa]
1	16.0	16.0	256.0	943000	36.8
2	16.2	16.2	262.4	1013000	38.6
3	16.1	16.0	257.6	941000	36.5
4	16.2	16.0	259.2	1009000	38.9
MEAN					37.7

Table 2 - RILEM three-point bending tests							
#	Weight [kg]	Length [mm]	Height [mm]	Depth [mm]	Span [mm]	Notch Length [mm]	Fracture Energy [N/m]
1	23.880	1000	100	100	800	49.5	137.1
2	24.040	1000	100	100	800	49.5	82.9
3	24.265	1000	100	100	800	51.0	96.3
4	23.690	1000	100	100	800	50.0	83.5
MEAN							100.0

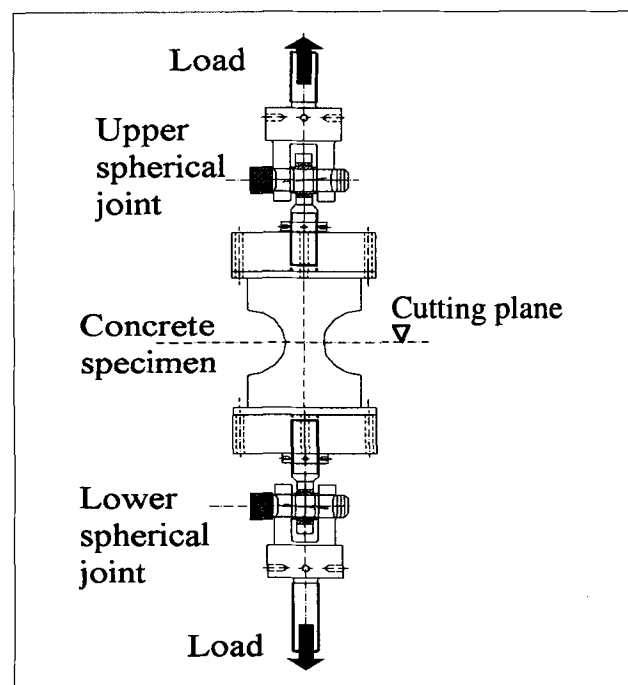


Fig. 1 - Diagram of the apparatus.

37.7 MPa, while the mean fracture energy is 100 N/m.

The complete mechanical characterization of the testing material is indispensable to a correct design of the displacement measurement bases (68 mm in our case), in order to avoid snap-back behaviours. The test apparatus scheme is shown in Fig. 1. The upper and the lower spherical hinges are realized with two SA 35 TE-2RS steel on teflon terminals (SKFTM). On one side, they are linked by a removable gudgeon to a crotch fixed to the MTSTM load actuator. On the other side, rigid thick platens are provided to connect the specimens. The concrete specimens (Fig. 3) are previously glued to two thin



Fig. 2 - Upper spherical hinge and rigid platen.

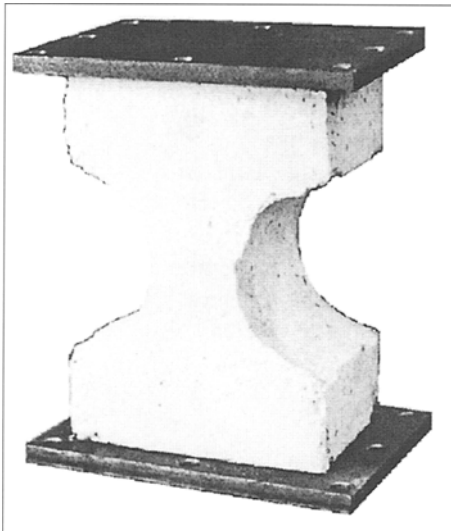


Fig. 3 - Dog-bone concrete specimen glued to the thin platens.

platens by using an epoxy two-component resin (Starcement 2XN by MPM™), that allows easy positioning and removal from the test apparatus.

To perform the displacement controlled tests, the mean value of four measurement bases was considered as feedback. Each displacement was acquired by DD1 displacement transducers, two for each side of the specimen, placed around the thinner zone, where damage localization is more likely to occur (Fig. 4). This choice allows also to evaluate the magnitude of flexural effects during the softening regime. In Fig. 5, a load-displacement curve is shown, with respect to the mean elongation as well as for each displacement acquisition. It is worth noting that a very small compression can be appreciated, confirming the efficiency of the collinear hinge mechanism.

In order to study the damage evolution by means of fractal concepts, the true stress-carrying cross sections referring to different levels of damage are to be compared. Therefore, specimens are grouped and subjected to increasing deformations, after the peak load is reached. The damage control variable D is equal to:

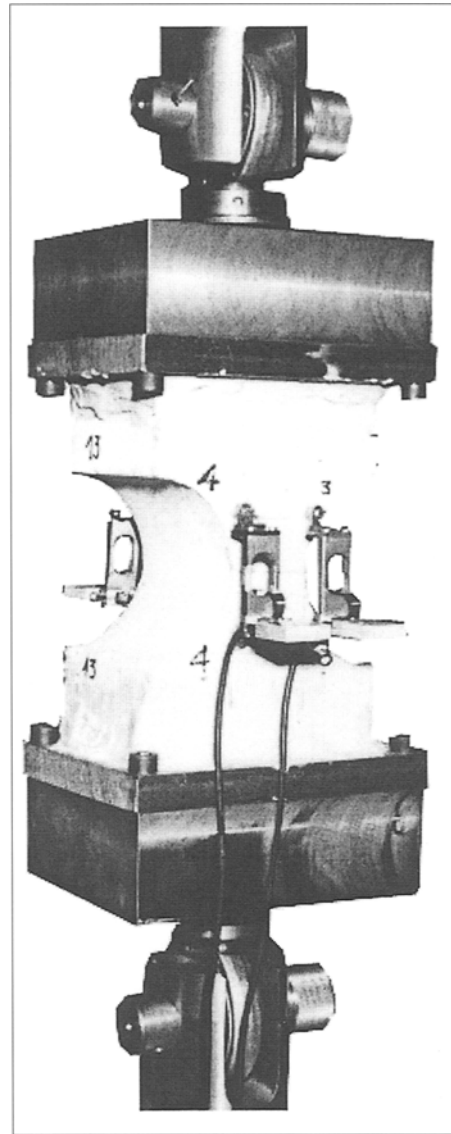


Fig. 4 - View of the test equipment.

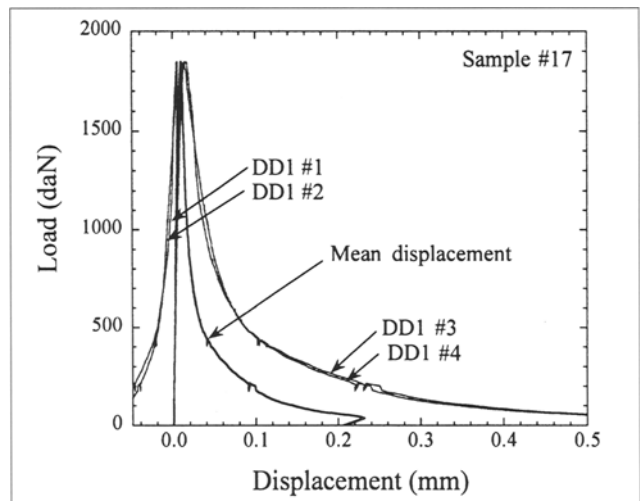


Fig. 5 - Load vs. displacement: four DD1 measurements and mean value.

$$D = 1 - \frac{P_u}{P_p} \quad (1)$$

where P_p is the peak load and P_u is the load reached just before unloading. In this way, damage is zero before the

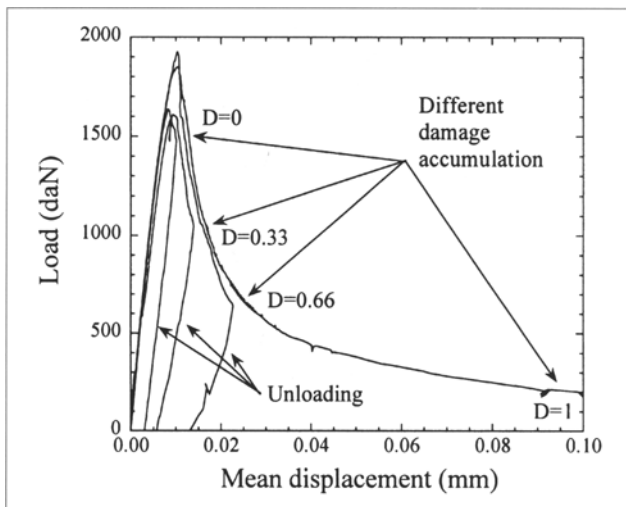


Fig. 6 - Different damage accumulation in the softening regime.

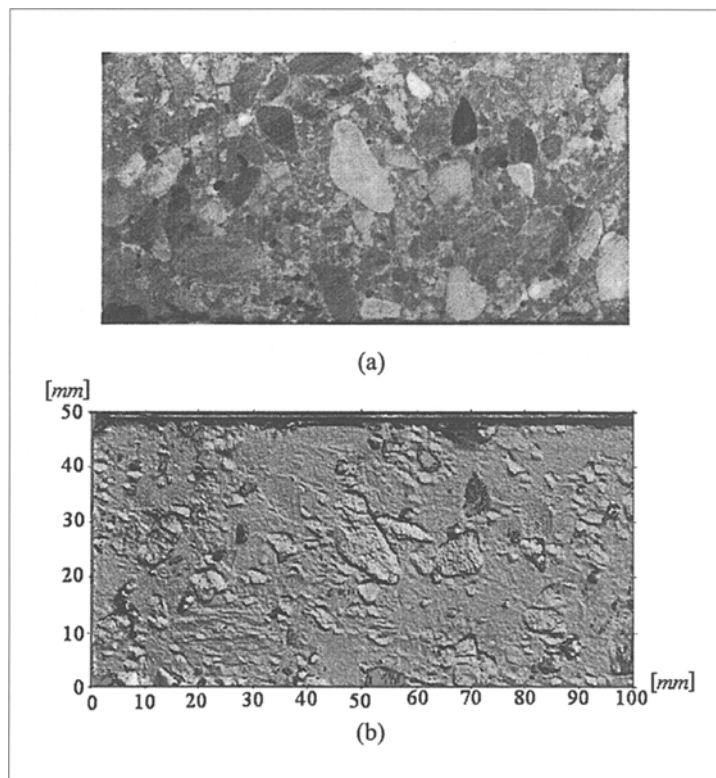


Fig. 7 - Traditional image analysis (a). Shaded relief restitution of the laser scanned surface (b).

peak load, increases descending along the softening curve, and is equal to one when the specimen is completely broken apart. Once a certain damage is accumulated in the specimen, the load has been removed. Four levels of damage have been chosen, ranging from undamaged material (just after the peak load) to the complete separation of the specimen into two halves, as shown in Fig. 6.

The mean tension strength of the specimens is equal to 3.55 MPa, with a standard deviation of 0.375 MPa. These results suggest that not a so dispersed value of tension strength is obtained when the tests are carried out properly.

3. THE LASER SCANNER ACQUISITION

The main purpose of the experimental methodology, entirely developed at Politecnico di Torino [1], is to digitize the three-dimensional topography of surfaces at the meso-scale. The surface height measurements are performed by means of a laser profilometer, counting the number of wave-cycles between the ray emission and the ray reception after the reflection on the specimen surface. The specimen to be analyzed is rigidly framed into a solid truss, whereas the horizontal position of the distanziometer is controlled by two orthogonal micrometric step motors. The step motors interface and the data acquisition board that convert the analogical signal provided by the laser are both plugged in the same PC motherboard. A dedicated software provides extreme versatility and the full automation of the surface acquisition process. The digitized surfaces can extend over a 50 mm × 100 mm area, and a 2 μm maximum precision can be achieved, both in the vertical and horizontal directions.

In the study of the microstructural morphology of concrete it is useful to digitize planar cross sections obtained by cross-cutting progressively damaged specimens (see the plane of cut in Fig. 1). These surfaces appear almost flat, with localized distribution of moon-like craters due to the intersection of the cutting plane with the inherent microstructural flaws. In Fig. 7a, one cross-cutting surface is shown and compared with the numerical shaded-relief restitution of the acquired topography of Fig. 7b. The presence of cavities is responsible for an effective resisting cross section that is less dense and compact than the nominal one. Furthermore, in real situations, the porosity is not uniform, and the relative percentage of voids depends on the linear size of the considered section. The true stressed domain is made out of points not belonging to the craters, *i.e.* to the pore structure. Hence, from a theoretical point of view, the true resisting section can be evaluated by considering the set of points whose heights are exactly equal to the cutting plane height.

Practically, the obtained surface is not plane and presents a low uniform roughness due to the cutting process that can be confused with the finer porosity. For this reason, another virtual plane has been considered, parallel to the cutting section, but at a lower height, which is able to intersect only the real cavities (Fig. 8). The points whose height is greater than the virtual plane height, are considered to belong to the real stress-carrying domain, while the remaining points belong to the (complementary) void set. This procedure allows to filter out the noise produced by cutting. However, some information is lost about the finer porosity. To perform the virtual cut, it is also necessary to determine the mean real cutting plane by a detrending algorithm. In Fig. 9, the theoretical evolution of the fractal dimension of the effective cross section is shown as a function of the virtual plane height, for increasingly damaged sections.

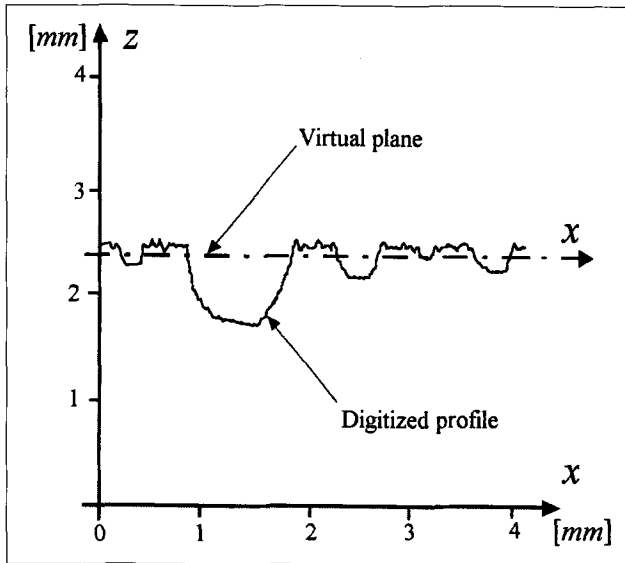


Fig. 8 - Scheme of the virtual section.

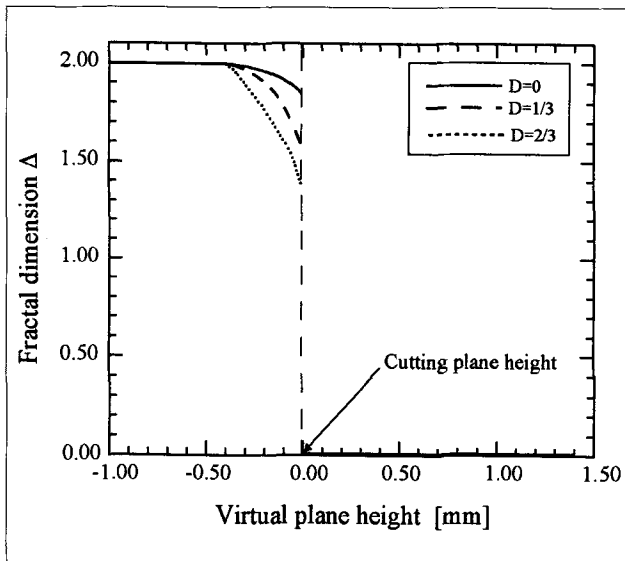


Fig. 9 - Expected theoretical evolution of the fractal dimension for growing damage level.

When the virtual plane lays well beneath the real cutting plane, no voids are intersected; consequently, the calculated dimension is equal to 2 (Euclidean). Increasing the virtual plane height, more and more voids are intersected, and the fractal dimension decreases approaching a limit value that depends on the rarefaction (and thus on the damage) of the section. As soon as the virtual plane height exceeds the real cutting plane height, the dimension falls down to zero, since there are no more intersected points at all.

4. THE FRACTAL ANALYSIS OF DAMAGED CROSS SECTIONS

The fractal dimension of the effective stress-carrying domain has been calculated by using two different algorithms. Based on the concept of covering, the box-counting method estimates the fractal dimension as a

function of the vanishing order of the covering area. The number of boxes N_i , needed to cover the set, is calculated for a decreasing value of the side d of the square covering element. The stress-carrying cross section is a self-similar lacunar fractal in a statistical sense. Then the following equation holds:

$$\Delta_{box} = \lim_{d \rightarrow 0} \frac{\log N_i}{\log(1/d)} \quad (2)$$

The fractal dimension can be also evaluated by referring to the mass logarithmic density. If the effective cross section were characterized by a uniform distribution of cavities, it would be possible to calculate the density defined as the ratio of the effective area A_{eff} to the nominal area A_{nom} . In the actual case, this density can not be unambiguously calculated, because it depends on the resolution and on the size of the considered area. In fact, the complex distribution of the pores causes the probability of finding large cavities to be higher as the size of the considered area increases (like in a natural sponge [11]). The classical density is not constant, but decreases by increasing the nominal size. To obtain a scale-invariant value, it is necessary to refer to the logarithmic density, which is defined as:

$$\rho_{log} = \frac{\log A_{eff}}{\log A_{nom}} \quad (3)$$

If d is the linear size of the considered area, the fractal dimension Δ_{log} can be evaluated as the limit slope of the bilogarithmic diagram $\log A_{eff}$ versus $\log d$. The fractal dimension calculation has been performed for each virtual plane position to obtain the curve of complete dimension evolution. Because of the cutting noise, the theoretical diagram of Fig. 9 can not be recovered exactly. Therefore, the experimental curves of Fig. 10 are characterized by a transition smoother than expected. Nevertheless, a general trend can be recognized, i.e. decreasing of the stress-carrying cross section fractal dimension for increasing damage levels.

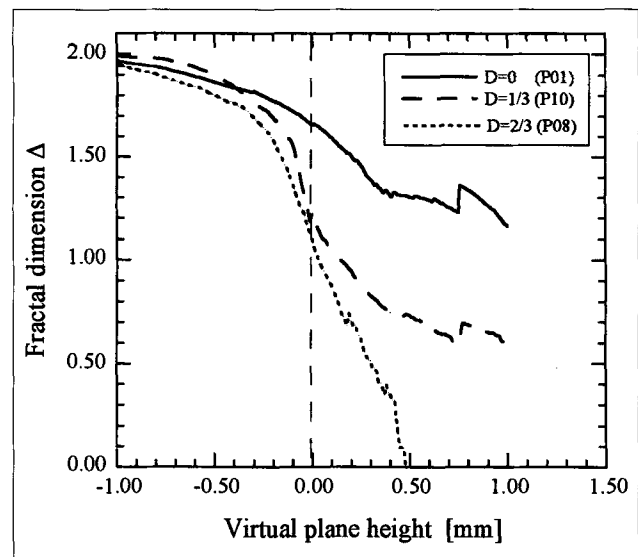


Fig. 10 - Experimental decrease of the stress-carrying cross section fractal dimension for increasing levels of damage.

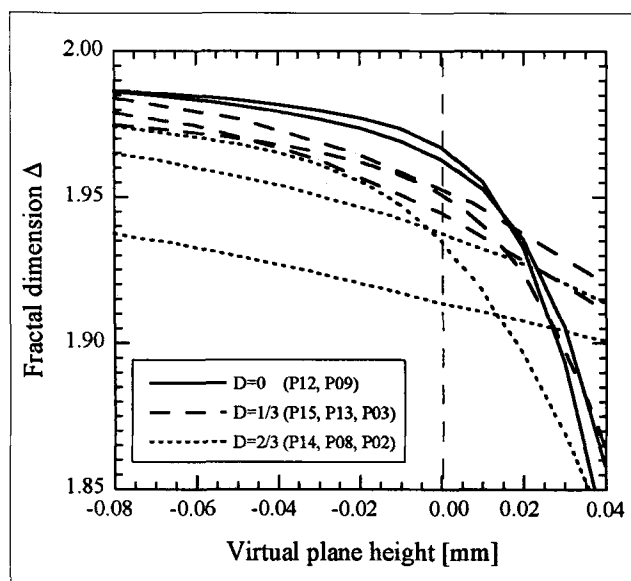


Fig. 11 – Detail of the fractal dimension curves for each specimen group (with different damage) near the theoretical discontinuity point (virtual plane height equal to zero).

In Fig. 11 the detail of the fractal dimension vs virtual plane height is shown for each specimen belonging to the three damage levels ($D = 0$, $D = 1/3$ and $D = 2/3$), in the neighbourhood of the $z = 0$ virtual plane. In spite of some statistical variations, each specimen group shows a decreasing fractal dimension of the effective area for increasing damage. The fractal dimension decrease seems to be very slow during the main part of the softening curve, while the dimension (as well as the measure) rapidly goes to zero when the specimen is finally broken apart. This suggests to assume the following power-law for the relation between the fractal dimension and the damage variable:

$$\Delta = \Delta_0(1 - D)^\gamma \quad (4)$$

where Δ_0 is the fractal dimension of the undamaged effective section ($\Delta_0 < 2$), and γ the exponent (very close to zero). The experimental fitting is shown in Fig. 12, where $\Delta_0 = 1.958$ and $\gamma = 0.011$.

It is worth noting that, while the decrease of the ligament measure is due to macro-fracture coalescence, the decrease of the fractal dimension is reasonably ascribed to the micro- and meso-fracture enucleation as well as to the evolution in inherent porosity.

5. CONCLUSIONS

A new direct tension test equipment has been developed that minimizes flexural effects on concrete dog-bone-shaped unnotched specimens. Progressively damaged specimens have been sawn and laser scanned in order to obtain the topography of the cut surface. This procedure allows to obtain the true stress-carrying domain. The damage evolution during the softening regime has been characterized by means of fractal geom-

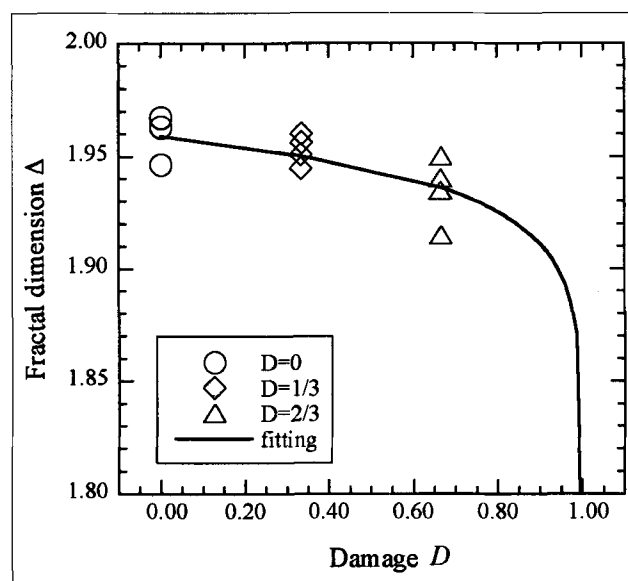


Fig. 12 – Nonlinear interpolation of the fractal dimension decrease as a function of damage.

etry. The general decreasing trend of the ligament fractal dimension with respect to increasing damage can be recognized rather easily. This dimension lowering is probably due to micro- and meso-fracture enucleation as well as to inherent porosity evolution, and has not to be confused with the classical measure decreasing, to be ascribed to macro-fracture propagation throughout the specimen. While the macro-fractures are detectable only in the final stage of the softening tail, the fracture enucleation (and then the dimension decreasing) seems to be a more progressive phenomenon. The main drawback appears to be the saw-cutting process. In order to confirm the proposed quantitative Δ vs. D relation between the ligament fractal dimension and the damage variable, an improvement of the present sawing technique should be realized.

ACKNOWLEDGEMENTS

The present research was carried out with the financial support of the Ministry of University and Scientific Research (MURST), the National Research Council (CNR) and the EC-TMR Contract No. ERBFMRXCT 960062. Thanks are also due to Mr. Vincenzo Di Vasto for carefully performing the testing programme.

REFERENCES

- [1] Carpinteri, A., Chiaia, B. and Invernizzi, S., 'Fracture behaviour of a solid with random porosity: experimental analysis and size effect', in Proceedings of the Twelfth European Conference on Fracture ECF12 - Fracture from Defects, Edited by M.W. Brown *et al.*, (Ems Publishing, London, 1998) III, 1557-1562.
- [2] Carpinteri, A., Chiaia, B. and Invernizzi, S., 'Three-dimensional fractal analysis of concrete fracture at the meso-level', *Theoretical and Applied Fracture Mechanics* 31 (1999) 163-172.

- [3] Carpinteri, A., 'Fractal nature of materials microstructure and size effects on apparent mechanical properties', *Mechanics of Materials* **18** (1994) 259-266.
- [4] Carpinteri, A., Ferro, G. and Invernizzi, S., 'The nominal tensile strength of disordered materials: a statistical fracture mechanics approach', *Engineering Fracture Mechanics* **58** (1997) 421-435.
- [5] Carpinteri, A. and Ferro, G., 'Size effects on tensile fracture properties: a unified explanation based on disorder and fractality of concrete microstructure', *Mater. Struct.* **27** (1994) 563-571.
- [6] Mechtcherine, V. and Müller, H. S., 'Effect of the test set-up on fracture mechanical parameters of concrete', Proceedings of FRAMCOS-3, Edited by H. Mihashi *et al.*, (Aedificatio Publishers, Freiburg, 1998) I 377-386.
- [7] Cattaneo, S. and Rosati, G., 'Effect of different boundary conditions in direct tensile tests: experimental results', *Magazine of Concrete Research* **51** (5) (1999) 365-374.
- [8] van Mier, J. G. M., Schlangen, E. and Vervuurt, A., 'Boundary and size effects in uniaxial tensile tests: a numerical and experimental study', in 'Fracture and Damage of Quasibrittle Structures', Edited by Z. P. Bažant *et al.* (E&FN Spon, London, 1994) 289-301.
- [9] van Vliet, M. R. A. and van Mier, J. G. M., 'Effect of strain gradients on the size effect of concrete in uniaxial tension', *International Journal of Fracture* **95** (1999) 195-219.
- [10] RILEM Technical Committee 50 'Determination of the fracture energy of mortar and concrete by means of three point bend tests on notched beams', *Mater. Struct.* **18** (1985) 287-290.
- [11] Mandelbrot, B. B., 'The Fractal Geometry of Nature', (W.H. Freeman & Co, San Francisco, 1982).

